

Coherent properties of single rare-earth spin qubits.

P. Siyushev,¹ K. Xia,¹ R. Reuter,¹ M. Jamali,¹ N. Zhao,² N. Yang,³

C. Duan,⁴ N. Kukharchyk,⁵ A.D. Wieck,⁵ R. Kolesov,¹ and J. Wrachtrup¹

¹*3. Physikalisches Institut, Universität Stuttgart and
Stuttgart Research Center of Photonic Engineering (SCoPE),
Pfaffenwaldring 57, Stuttgart, D-70569, Germany*

²*Beijing Computational Science Research Center, Beijing 100084, China*

³*Institute of Applied Physics and Computational Mathematics,
P.O. Box 8009(28), 100088 Beijing, China*

⁴*Hefei National Laboratory for Physics Sciences at Microscale and Department of Physics,
University of Science and Technology of China, Hefei, 230026, China*

⁵*Ruhr-Universität Bochum, Universitätsstraße 150 Gebäude NB, D-44780 Bochum, Germany*

Rare-earth-doped crystals are excellent hardware for quantum storage of optical information [1–3]. Additional functionality of these materials is added by their waveguiding properties [4, 5] allowing for on-chip photonic networks. However, detection and coherent properties of rare-earth single-spin qubits have not been demonstrated so far. Here, we present experimental results on high-fidelity optical initialization, efficient coherent manipulation, and optical readout of a single electron spin of Ce^{3+} ion in a YAG crystal. Under dynamic decoupling [6], spin coherence lifetime reaches $T_2 = 2\text{ ms}$ and is almost limited by the measured spin-lattice relaxation time $T_1 = 3.8\text{ ms}$. Strong hyperfine coupling to aluminium nuclear spins suggests that cerium electron spins can be exploited as an interface between photons and long-lived nuclear spin memory. Combined with high brightness of Ce^{3+} emission and a possibility of creating photonic circuits out of the host material, this makes cerium spins an interesting option for integrated quantum photonics.

Outstandingly long spin coherence times of rare-earth-based optical crystals result in long-lasting memories for storing quantum states of single photons [7] as well as the states of entangled photon pairs [8, 9]. In these quantum memories the quantum state of a photon is stored in an electron or nuclear spin wave created in an ensemble of spins. This type of memory is an essential ingredient of quantum repeaters [10] and quantum computing protocols based on linear optics [11]. However, ensemble-based rare-earth quantum computer designs lack scalability [12] in a sense that the number of interacting qubits is strictly limited by the number of spin states. This problem can be resolved by addressing single rare-earth spins individually. In the last two years, detection of several rare-earth species in a crystal host at a single ion level was demonstrated [13–15] though no long-lasting spin coherence was demonstrated so far. In this Letter, we present for the first time optical initialization, coherent manipulation, and optical readout of a single cerium ion in a crystalline host.

Experimentally, individual cerium ions were identified in an ultra-pure YAG crystal by confocal microscopy [15] at $T \approx 3.5\text{ K}$ (see Methods section and Supplementary Figure S1). In order to improve the fluorescence collection efficiency of the microscope, a solid immersion lens (SIL) was fabricated on the surface of the sample by focused ion beam milling. Cerium emission associated with the $5d \rightarrow 4f$ (see Figure 1a) transition was excited by a frequency-doubled femtosecond Ti:Sapphire laser at 460 nm and detected in $475\text{--}630\text{ nm}$ spectral window. The image of individual cerium ions under the SIL is shown in Figure 1b. The detected emission of an individual cerium ion amounts to $60 - 70 \times 10^3\text{ photons/s}$. The emission spectrum of the ions is indicated in Figure 1c showing broadband phonon-assisted emission and a sharp zero-phonon line at 489 nm characteristic for cerium ions [16]. Cerium fluorescent centres can be created in YAG crystal by ion implantation (see Figure 1d). Comparing the brightness of a single cerium ion and that of the implanted regions and assuming the implantation dose to be known (though the dose is believed to be significantly overestimated), we obtained the lower boundary of the implantation yield of 8%. The electronic level structure of cerium substitutional impurities in ceramic crystals is shown in Figure 1a. The strongest transition between the ground $4f(1)$ and the optically excited $5d(1)$ spin doublets under σ^+ circularly polarized excitation is the a spin flip transition $|4f(1) \downarrow\rangle \rightarrow |4d(1) \uparrow\rangle$. The other 3 transitions are almost 3 orders of magnitude weaker [15]. However, the decay back to the ground state is equally probable. This results in efficient pumping of the ion into spin-up “dark” state. In this way, cerium spin state can be initialized. To reveal pumping dynamics of cerium spin, magnetic field of 490 G parallel to the excitation beam was applied to the sample, the excitation laser was chopped such that the cerium centre is excited with a finite train of pulses and the time

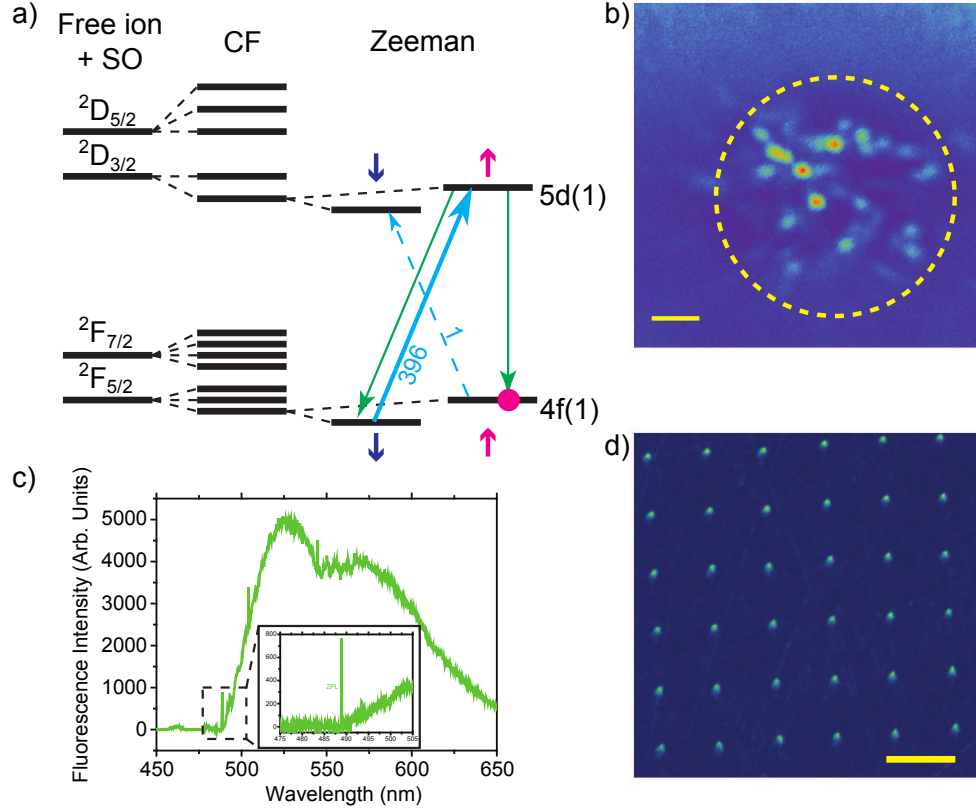


FIG. 1. **General properties of a single Ce^{3+} ion in YAG.** a) Electronic level structure of Ce^{3+} ion in YAG crystal. Relative strengths of optical transitions between the lowest 4f and the lowest 5d spin doublets (396:1) are shown for circularly polarized excitation light propagating along the y-axis of the local Ce^{3+} symmetry frame. External magnetic field along the same direction splits the spin doublets. b) Confocal scan of individual cerium centres under the SIL. The scale bar is 2 μm . The dashed circle indicates the boundary of the SIL. c) Typical spectrum of a single cerium ion. The inset shows a zoom into the ZPL of Ce^{3+} . The positions of ZPLs for distinct cerium centres are slightly different depending on the local environment of each centre. d) Focused beam of cerium ions accelerated to 300 keV was used to create a grid of fluorescent spots in YAG single crystal. The scale bar is 10 μm . Measurements of fluorescence lifetime, spectra, and excited state Larmor precession proved that the fluorescence originates from substitutional Ce^{3+} ions in YAG.

evolution of the excited fluorescence was investigated (see Figure 2a). As shown in Figure 2b, right after the circularly polarized excitation is switched on, the emission intensity is maximal determined by thermalized populations of the ground-state spin sublevels. It rapidly drops due to optical pumping into the “dark” spin state. The ratio of the fluorescence intensities in the beginning of the fluorescence decay and after the spin is polarized indicates $> 97\%$ fidelity of spin initialization. The fidelity of spin initialization not reaching the theoretically predicted ratio 396 : 1

is thought to be due to slight ellipticity of the polarization caused by non-perfect $\lambda/4$ waveplate and polarization distortion due to SIL. Under linearly polarized excitation, cerium emission does not depend on time indicating the absence of optical pumping. The dependence of the emission on the ellipticity of the excitation is given in Supplementary Figure S2.

The lifetime of the initialized spin state T_1 was measured by introducing the second (readout) train of laser pulses having the same circular polarization and varying the time interval between initialization and readout (see Figure 2c). The fluorescence recovery indicates thermalization of the spin states. The measurement resulted in the spin relaxation time of $T_1 = 3.8 \text{ ms}$ (see Figure 2d).

The initialized spin can be manipulated by microwave radiation resonant with the spin transition

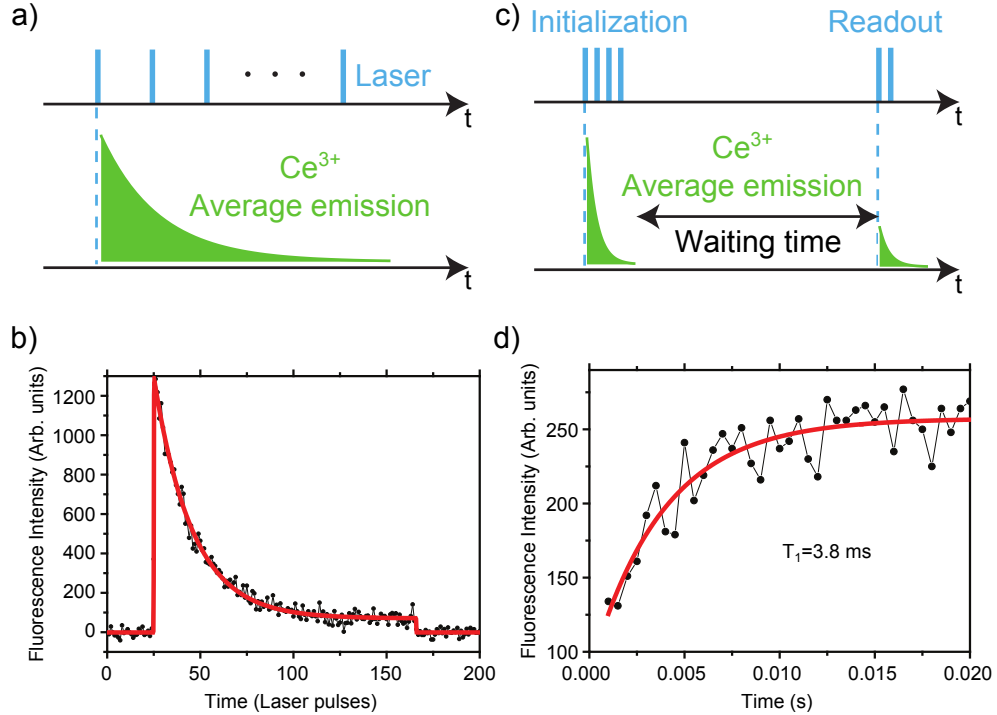


FIG. 2. **Initialization and thermalization of Ce^{3+} spin.** a) Schematic diagram of the laser pulse sequence used to study the initialization dynamics. The time interval between the trains was chosen to be long enough for the spin population to thermalize. The photons accumulated after each pulse in the train are summed up and represent one point on the initialization fluorescence curve. b) Experimental dependence of the fluorescence on time during initialization process. c) Laser pulse sequence used to measure spin T_1 time. The initializing pulse train is long (around 50 pulses) to ensure spin polarization. The readout pulse train contains only 5 pulses. The time interval between initializing the spin and reading it out is varied. d) Spin relaxation curve recorded by detecting the fluorescence during the readout pulse train.

of the ground $4f(1)$ state. For that purpose, a microwave structure was created on the surface of the sample right next to the location of the SIL. This allowed us to record optically detected magnetic resonance (ODMR) spectra of individual cerium ions. Once the frequency of microwaves matches that of the spin transition, the population from the $|4f(1) \uparrow\rangle$ state is pumped back into $|4f(1) \downarrow\rangle$ and the overall fluorescence yield increases. Typical ODMR spectrum of a single cerium ion is shown in Figure 3a. Linewidths of ODMR spectra are in the range of $10 - 15 \text{ MHz}$ varying slightly for different cerium centres. Since Ce^{3+} can occupy 6 magnetically inequivalent sites in YAG, in general, 6 distinct positions of ODMR peak are possible. A combination of measured ODMR frequency and of known g-tensor of ground-state Ce^{3+} spin [17] allowed us to determine the orientation of individual cerium sites. In our (110) oriented crystal, the ODMR resonances were at 650 MHz , 1310 MHz and four nearly degenerate ones around 1550 MHz . For further experiments we were choosing the centres having their local y-axis oriented along the magnetic field and the excitation beam (640 MHz) since for these centres the theoretical predictions for spin initialization fidelity is the best. The first step towards coherent manipulation of cerium electron spin is detection of Rabi oscillations under strong microwave driving. Experimentally, circularly polarized laser excitation was chopped such that only a few tens of laser pulses are used to initialize the spin in $|4f(1) \uparrow\rangle$. After this laser pulse train, a microwave pulse at resonant frequency of variable duration was applied (see Figure 3b). Finally, a short laser pulse train consisting of 2-5 pulses having the same circular polarization was applied to read out the population of spin state $|4f(1) \downarrow\rangle$. The result of the measurement is shown in Figure 3c. The frequency of Rabi oscillations has square-root dependence on the microwave power. The decay time of oscillations is longer than that determined by the inhomogeneous linewidth indicating partial locking of the spin by microwaves.

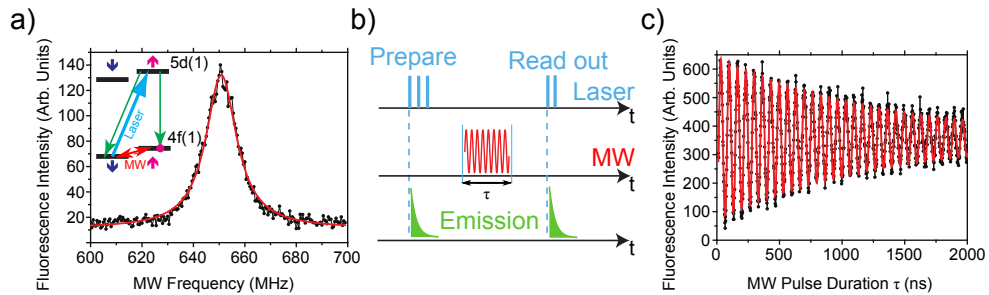


FIG. 3. **Coherent manipulation of Ce^{3+} spin.** a) ODMR signal of a single Ce^{3+} ion. Inset shows level structure of the ground-state and the optically excited spin doublets. b) Schematic diagram of Rabi measurements. c) MW Rabi oscillations of a single Ce^{3+} spin.

Dephasing of cerium spin was determined by measuring the decay of Hahn echo signal (a sequence of $\pi/2 - \tau - \pi - \tau - \pi/2$ microwave pulses, see inset in Figure 4a). The result yields a value of $T_2 = 2\tau = 240 \text{ ns}$. Fast decoherence in YAG can be explained by the presence of the dense bath of ^{27}Al having spin of $I = 5/2$ accompanied by large magnetic moment $\mu_{\text{Al}} = 3.64\mu_N$ with μ_N being nuclear magneton. Fluctuating nuclear spins produce magnetic noise at the location of Ce^{3+} reducing the coherence time. Theoretical analysis of the nuclear spin bath showed that the contribution of octahedrally coordinated ^{27}Al nuclei to decoherence is the largest (see Supplementary Methods).

Dynamic decoupling exploiting sequences of π microwave pulses allows for enormous increase in decoherence time. Decoherence is caused by the averaging over a phase factor $C(t) = \langle e^{i\varphi(t)} \rangle$ the Ce^{3+} spin acquires during free evolution. π pulses applied with frequency $1/\tau$ effectively eliminate noise spectral components $\nu_{\text{noise}} < 1/\tau$ and thus lead to lengthening of coherence lifetime. We used Carr-Purcell-Meiboom-Gill (CPMG) microwave decoupling sequence [18, 19] (see Figure 4b). The maximum number of refocusing pulses applied was 24576. This allowed us to extend decoherence time to 1.97 ms . The measured CPMG-echo signals shown in Figure 4c agree well with the ones simulated by correlated cluster expansion method [20] (see Supplementary Figure S3). The dependence of the decoherence time on the number of CPMG pulses allows one to discriminate the influence of nuclear and electronic spin baths. The latter is composed of the spins of residual transition metal impurities such as Cr^{3+} and Fe^{3+} . Electron and nuclear spin baths have significantly different noise spectral densities. The noise of the electron spin bath is best described by a lorentzian shaped spectrum characterized by a long spectral tail. This leads to a $N^{2/3}$ dependence of the coherence time [21]. On the other hand, nuclear spin noise is characterized by a much harder cut-off leading to a linear dependence of T_2 on N . The experimentally measured dependence shown on Figure 4d is $T_2 \propto N^{0.88}$ indicating that both nuclear and electron spin baths lead to decoherence with former contribution prevailing. Stretched exponential fits ($\exp(-(t/T_2)^k)$) to CPMG-echo signals result in exponentials k between 6 and 12 confirming the existence of hard cutoff of the nuclear spin noise spectrum as described in Supplementary Methods. These results suggest that changing the host material to a low nuclear spin one, e.g. yttrium orthosilicate (YSO) in which rare-earth ions show the longest coherence and population lifetimes [2, 22, 23], should greatly increase coherence lifetime. Changing the host material has almost no effect on the atomic-like polarization selection rules of Ce^{3+} crucial for initializing its spin state. Our preliminary measurements show extended coherence lifetime in the excited $5d$ state in YSO compared to the YAG host (see Supplementary Figure S4).

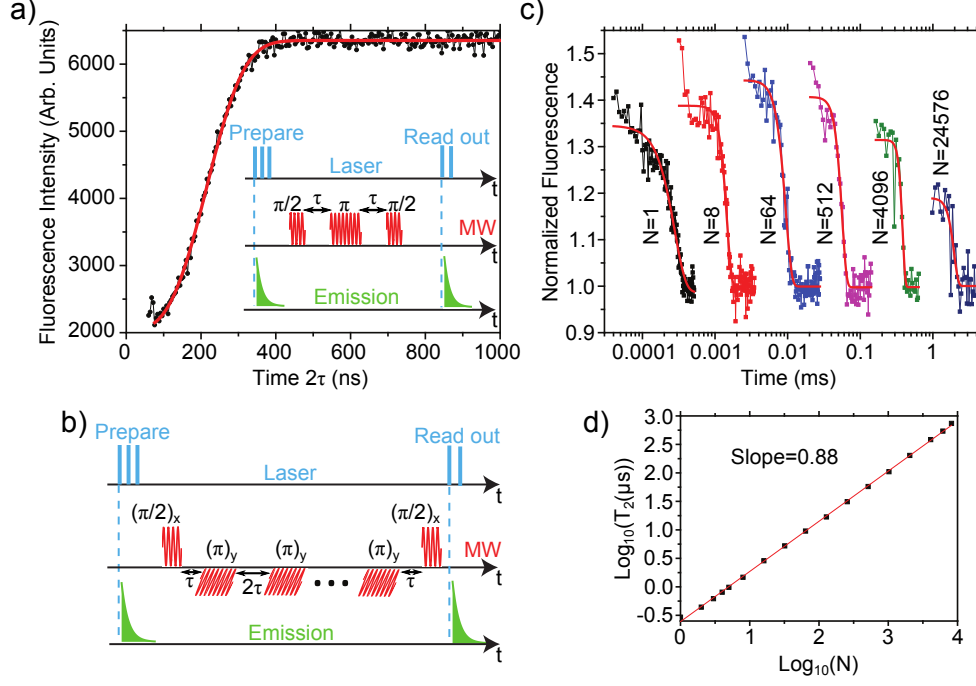


FIG. 4. **Dynamic decoupling of Ce^{3+} spin from the spin bath.** a) Spin-echo decay shows the decoherence time $T_2 = 240$ ns. The decay is non-exponential. b) Schematic diagram of measuring the decoherence time with CPMG decoupling sequence. After applying the first $\pi/2$ microwave pulse (X $\pi/2$ -pulse) and waiting for time τ , one applies a sequence of π -microwave refocusing pulses separated by 2τ from each other and phase-shifted from the X $\pi/2$ -pulse by 90° (Y π -pulses). Rotation in the Y- instead of the X-plane on the Bloch sphere makes the sequence robust against slight deviations of the refocusing pulses from π area. Finally, the degree of coherence can be tested by applying a second X $\pi/2$ -pulse and reading out the population in the “bright” spin state with the readout laser pulse train. c) Results of CPMG measurements for several sequences. The number of pulses for each sequence is given next to the corresponding decay curve. d) The dependence of the coherence lifetime on the length of CPMG sequence. The slope of 0.88 is closer to the linear dependence characteristic to nuclear spin bath rather than to $N^{2/3}$ characteristic to the electron spin bath.

In conclusion, we have demonstrated optically addressable rare-earth spin qubit in a ceramic crystal. Technologically advantageous feature of these materials is a possibility of creating them in a form suitable for integrated photonic circuit fabrication, e.g. in the form of thin films on low refractive index substrates (quartz). Subsequent FIB milling would allow for creating on-chip photonic circuits with low attenuation (1.5 dB/cm [4]) for single photons which would include waveguides, cavities, etc. This would result in technologically simple realization of a lab-on-chip approach for cerium spin qubits and, simultaneously, in obtaining an access to longer-living isolated nuclear spins magnetically coupled the electron spin of Ce^{3+} .

METHODS

Experimental Setup

Optical studies of single Ce^{3+} ions were performed in a home-built confocal microscope in which the crystal was mounted on a cold finger of a helium flow cryostat. An optical access was arranged through a window. The microscope objective lens of NA 0.95 was mounted inside the cryostat on a piezo nano-positioner. A toroidal permanent magnet was fixed onto the objective lens to provide magnetic field parallel to the propagation direction of the excitation laser beam. The fluorescence of cerium ions was collected by the same objective lens and detected with a single photon counting avalanche photodiode. In order to measure the emission spectra, the fluorescence was deflected by a mirror mounted on a flip mount onto a grating spectrometer equipped with a cooled CCD camera. For measurements involving microwaves, a high power MW amplifier (50 dB amplification, 30 W maximum output power) was used. The frequency of microwaves was swept by a software-controlled MW synthesizer.

Sample Preparation

In order to improve fluorescence collection efficiency, a solid immersion microlens was fabricated directly on the surface of the sample by focused ion beam milling. The lens had a shape of half-a-sphere with the radius of 5 μm . In order to perform spin manipulations with microwaves, a copper microwave structure was created next to the location of the SIL by lithographic means. Even though the microwave structure was not impedance-matched to the outer MW network, the measured overall MW loss amounted to only 6 dB.

-
- [1] Longdell, J.J., Fraval, E., Sellars, M.J., and Manson, N.B. Stopped Light with Storage Times Greater than One Second Using Electromagnetically Induced Transparency in a Solid. *Phys. Rev. Lett.* **95**, 063601 (2005)
 - [2] Heinze, G., Hubrich, C., and Halfmann, T. Stopped Light and Image Storage by Electromagnetically Induced Transparency up to the Regime of One Minute. *Phys. Rev. Lett.* **111**, 033601 (2013)
 - [3] Vivoli, V.C., Sangouard, N., Afzelius, M. and Gisin, N. High-bandwidth quantum memory protocol for storing single photons in rare-earth doped crystals. *New Journal of Physics* **15**, 095012 (2013)
 - [4] Wu, Y.-C., Parola, S., Marty, O., Villanueva-Ibanez, M., and Mugnier, J. Structural characterizations and waveguiding properties of YAG thin films obtained by different solgel processes. *Optical Materials*

- 27**, 1471-1479 (2005)
- [5] Kumari, S. and Khare, A. Optical and structural characterization of pulsed laser deposited ruby thin films for temperature sensing application. *Applied Surface Science* **265**, 180-186 (2013)
 - [6] Viola, L. and Lloyd, S. Dynamical suppression of decoherence in two-state quantum systems. *Phys. Rev. A* **58**, 2733-2744 (1998)
 - [7] de Riedmatten, H., Afzelius, M., Staudt, M.U., Simon, C., and Gisin, N., A solid-state lightmatter interface at the single-photon level. *Nature* **456**, 773-777 (2008)
 - [8] Clausen, C., Usmani, I., Bussieres, F., Sangouard, N., Afzelius, M., de Riedmatten, H., and Gisin, N. Quantum storage of photonic entanglement in a crystal. *Nature* **469** 508-511 (2011)
 - [9] Saglamyurek, E., Sinclair, N., Jin, J., Slater, J.A., Oblak, D., Bussieres, F., George, M., Ricken, R., Sohler, W., and Tittel, W. Broadband waveguide quantum memory for entangled photons. *Nature* **469**, 512-515 (2011)
 - [10] Sangouard, N., Simon, C., de Riedmatten, H. and Gisin N. Quantum repeaters based on atomic ensembles and linear optics. *Rev. Mod. Phys.* **83**, 33-80 (2011)
 - [11] Knill, E., Laflamme, R. and Milburn, G.J. A scheme for efficient quantum computation with linear optics. *Nature* **409**, 46-52 (2001)
 - [12] Longdell, J.J., Sellars, M.J. and Manson, N.B. Demonstration of Conditional Quantum Phase Shift Between Ions in a Solid. *Phys. Rev. Lett.* **93**, 130503 (2004)
 - [13] Kolesov, R., Xia, K., Reuter, R., Sthr, R., Zappe, A., Meijer, J., Hemmer, P.R., and Wrachtrup, J. Optical detection of a single rare-earth ion in a crystal. *Nature Communications* **3**, 1029 (2012)
 - [14] Yin, C., Rancic, M., de Boo, G.G., Stavrias, N., McCallum, J.C., Sellars, M.J. and Rogge, S. Optical addressing of an individual erbium ion in silicon. *Nature* **497**, 91-94 (2013)
 - [15] Kolesov, R., Xia, K., Reuter, R., Jamali, M., Sthr, R., Inal, T., Siyushev, P. and Wrachtrup, J. Mapping Spin Coherence of a Single Rare-Earth Ion in a Crystal onto a Single Photon Polarization State. *Phys. Rev. Lett.* **111**, 120502 (2013)
 - [16] Robbins, D.J. *J. Electrochem. Soc.* **126**, 1550-1555 (1979).
 - [17] Lewis, H.R. Paramagnetic Resonance of Ce^{3+} in Yttrium Aluminum Garnet. *J. Appl. Phys.* **37**, 739-741 (1966)
 - [18] Carr, H.Y. and Purcell, E.M. Effects of Diffusion on Free Precession in Nuclear Magnetic Resonance Experiments. *Phys. Rev.* **94**, 630-638 (1954)
 - [19] Meiboom, S. and Gill, D. Modified SpinEcho Method for Measuring Nuclear Relaxation Times. *Rev. Sci. Instrum.* **29**, 688-691 (1958)
 - [20] Yang, W. and Liu, R.-B. Quantum many-body theory of qubit decoherence in a finite-size spin bath. *Phys. Rev. B* **78**, 085315 (2008)
 - [21] de Lange, G., Wang, Z.H., Risté, D., Dobrovitski, V.V. and Hanson, R. Universal Dynamical Decoupling of a Single Solid-State Spin from a Spin Bath. *Science* **330**, 60-63 (2010)

- [22] Yan, Y., Karlsson, J., Rippe, L., Walther, A., Serrano, D., Lindgren, D., Pistol, M.E., Kröll, S., Goldner, P., Zheng, L., and Xu, J. Measurement of linewidths and permanent electric dipole moment change of the $Ce\ 4f-5d$ transition in Y_2SiO_5 for qubit readout scheme in rare-earth ion based quantum computing. *Phys. Rev. B* **87**, 184205 (2013)
- [23] Könz, F., Sun, Y., Thiel, C.W., Cone, R.L., Equall, R.W., Hutcheson, R.L., and Macfarlane, R.M. Temperature and concentration dependence of optical dephasing, spectral-hole lifetime, and anisotropic absorption in $Eu^{3+} : Y_2SiO_5$. *Phys. Rev. B* **68**, 085109 (2003)